

Factor Analysis of Pavement Distresses for Surface Condition Predictions



Ontario

Ministry of
Transportation and
Communications

Research and
Development
Branch

Technical Report Documentation Page

Factor Analysis of Pavement Distresses for Surface Condition Predictions

Authors:	J.J. Hajek, Project Research Engineer, Research & Development Branch, MTC R.C.G. Haas, Chairman and Professor, Dept. of Civil Engineering, U. of Waterloo
MTC No.:	PAV-86-04
Published by:	The Research and Development Branch Ontario Ministry of Transportation and Communications
Participating Agencies/- Client:	N/A
Abstract:	Pavement distress information is needed to assess maintenance requirements and to plan rehabilitation. For immediate maintenance requirements, it is necessary that the details of individual distress types, severity, and density be known. However, for pavement design and long-range rehabilitation planning, more approximate and aggregated data are sufficient. Furthermore, due to correlation between individual distresses, it is only practical to predict aggregated rather than individual, detailed distresses. The Ontario Ministry of Transportation and Communications (MTC) currently uses 15 pavement surface distress types characterized by five levels of severity and five levels of density, in their condition survey procedures for flexible pavements. This paper describes how they were integrated into five, fundamental uncorrelated categories or factors using factor analysis techniques. The five factors are: • thermal cracking, • edge cracking, • surface instability, • fatigue cracking, and • random cracking. Analyses were based on data observed on about 350 pavement sections. In general, the pavement structure of these sections consisted of asphalt concrete on top of granular materials. The results showed that, of the variance associated with the original 15 distress types, about 60% could be explained by the five, fundamental factors. These five, basic, uncorrelated factors will be used for future surface distress predictions rather than the original 15 types measured in distress surveys. However, the 15 individual distress types are still required for the selection of specific maintenance treatments and for establishing the existing values of the five factors.
Comments:	Prepared for presentation at the annual meeting of the Transportation Research Board, Washington, D.C., January 1987.
Key words:	factor analysis, pavement evaluation and rating, damage attributes, prediction of pavement performance
Distribution:	One hundred copies distributed at TRB, others on request to pavement design and maintenance engineers.
Copyright Status:	Crown copyright

Factor Analysis of Pavement Distresses for Surface Condition Predictions

J.J. Hajek
Project Research Engineer
Research and Development Branch, MTC

R.C.G. Haas
Chairman and Professor
University of Waterloo

Published by
The Research and Development Branch
Ontario Ministry of Transportation and Communications
Hon. Ed Fulton, Minister
D.G. Hobbs, Deputy Minister

Published without prejudice as to the application
of the findings. Crown copyright reserved; however,
this document may be reproduced for non-commercial
purposes with attribution to the Ministry.

For additional copies, write:
The Editor, Technical Publications
Room 320, Central Building
1201 Wilson Avenue
Downsview, Ontario
Canada M3M 1J8

Telephone: (416) 248-7226
CNCP Dialcom Electronic Mail: 21:MIN006

November 1986

Table of Contents
Tables and Figures

Introduction	1	Tables	
Interdependency of Distresses	1	1/ Simple Correlation Matrix for MTC's 15 Distress Manifestations	18
Factor Analysis Techniques	3	2/ Varimax Solution for Principal Component Analysis	19
Data Analysis	6	3/ Salient Factor Loadings	20
Interpretation of Factors	8	4/ Scoring Coefficients	21
Factor Scores	12		
Conclusions and Recommendations	14	Figures	
Acknowledgements	15	1/ Occurrence of Distress Manifestations	22
References	16	2/ Graphical Representation of Varimax Rotation	23

INTRODUCTION

Because pavements deteriorate with time, traffic and climate, it is not only the investment today which is important, but also its future preservation through timely maintenance and rehabilitation. Surface distress manifestations, and their quantification, plus measurements of surface roughness, structural adequacy and friction, provide us with much of the information to determine present and future needs and to plan maintenance and rehabilitation.

Distress manifestations are defined as visible consequences of various mechanisms which usually lead to a reduction in pavement performance [1]. At present, the Ontario Ministry of Transportation and Communications (MTC) uses 15 distress manifestations, listed in Table 1, to visually characterize pavement condition and to calculate Distress Manifestation Index as a measure of pavement structural performance [2].

While each of the 15 distress manifestations describes a unique or at least different visual pattern or characteristic, all 15 distresses still describe the same general phenomenon, that of pavement deterioration. As subsequently shown, the distress manifestations are interrelated and many are statistically highly correlated.

The principal objective of the research reported herein was to investigate if it is possible to identify some fundamental categories of distress manifestations and thus to simplify the existing method of describing and analysing pavement distresses. The original impetus for this work was a need to develop a simplified method for describing and predicting distress manifestations, and for identification of pavement failure modes which would serve the needs of an "expert system" for selection of pavement preservation treatments [3]. However, this paper is mainly concerned with how the simplified method of describing pavement distress manifestations can be used for prediction of pavement performance.

INTERDEPENDENCY OF DISTRESSES

In order to illustrate statistical dependence between the 15 distress manifestation characteristics, a correlation matrix of these distresses, based on

about 350 observations representing nearly all pavement management sections in three MTC Districts (Huntsville, Kingston and Stratford), is presented in Table 1. The section lengths ranged from 0.3 to 25.7 km with an average of 9.9 km. The sections were selected to exhibit a uniform pavement performance. The distresses were identified and rated by using the procedures described in Reference 2, and were measured in terms of their density and severity on interval and ordinal scales, respectively [4]. In both cases, the scale values ranged from 0 to 5. Final values of the distress manifestation variables were obtained by adding scaled values of density and severity. For example, if the severity of wheel track rutting was moderate (i.e., rutting depth was in the range of 12 to 19 mm) and its density was throughout (i.e., moderate rutting occurred on 80 to 100% of the section length), the severity was assigned a value of 3, the density a value of 5, and the final value was 8. This procedure was originally developed for calculation of Distress Manifestation Index [2].

The coefficients of the correlation matrix for the 15 variables (Table 1) appear reasonable and as expected in both sign and magnitude. For example, variable B, flushing, is positively correlated with variable E, distortion ($r = 0.316$). This correlation suggests that excess asphalt, which results in flushing also contributes to distortion. On the other hand, the lack of significant correlation between flushing and variable L (single and multiple transverse cracking), $r = -0.002$, suggests the flushing does not have any effect on the formation of transverse cracks.

Detailed examination of the correlation matrix suggests that the distresses are highly correlated in many complex ways. For example, half, full and multiple transverse cracking have statistically significant correlations with, among others:

- wheel track rutting ($r = 0.40$)
- single and multiple longitudinal wheel track cracking ($r = 0.42$)
- single and multiple centreline cracking ($r = 0.59$), and
- longitudinal meander and midlane cracking ($r = 0.43$).

Continuing with the example, wheel track rutting has, in turn, statistically significant correlation with yet other distresses such as distortion ($r = 0.31$).

Variables which are highly correlated may actually measure similar characteristics and may be interchangeable to a certain degree. Also, correlation between variables masks specific influences of individual variables and often prevents their use in multiple regression models, particularly those obtained by stepwise regression.

A question then arises: What is the minimum number of distresses (variables) capable of describing distress manifestations in a concise, elucidative manner? Preferably, these variables should be uncorrelated and should attempt to identify fundamental distress categories.

The task of summarizing interrelationships among many variables in a concise basic manner can be tackled very effectively by factor analysis techniques [5,6]. These techniques were first applied in the area of psychology in the early 1900s. Since the 1940s, factor analysis has been used in many other fields such as sociology, medicine, business and even transportation planning [7]. However, it appears that this technique has seen limited, if any, application to pavement technology.

FACTOR ANALYSIS TECHNIQUES

The basic factor model represents variables as additive composites of several weighted factors or loadings using a set of linear equations called the total factor pattern:

$$\begin{aligned} Z_1 &= a_{11}F_1 + a_{12}F_2 + \dots a_{1m}F_m + b_1S_1 + e_1E_1 \\ Z_2 &= a_{21}F_1 + a_{22}F_2 + \dots a_{2m}F_m + b_2S_2 + e_2E_2 \\ &\vdots \\ Z_n &= a_{n1}F_1 + a_{n2}F_2 + \dots a_{nm}F_m + b_nS_n + e_nE_n \end{aligned} \quad (1)$$

where, using index j to designate variables and index i to designate individuals (observations):

Z_j = Observed variable; total number of variables being n .

F_j = New, uncorrelated components called common factors.

The total number of common factors is m and is usually much smaller than n . F_j is a factor common to all variables.

S_j = Specific factor
 E_j = Error factor; ($S_j + E_j$) are called unique factors
 a_{ji} = Common factor coefficients; $a_{ji}F_j$ is the contribution of the F_j factor to the linear composite
 b_j = Specific factor coefficient
 e_j = Error factor coefficient

The factor analysis model resembles that of regression analysis insofar as a variable is described as a linear combination of another set of variables plus a residual. However, in regression analysis this set of variables (i.e., the set of independent variables) are observable quantities, while in factor analysis they are hypothetical constructs which can only be estimated from the observed data [6]. The important property of factors as hypothetical constructs is that they are independent (and uncorrelated) even though the original variables themselves may be related.

The objective of factoring, which constitutes the basic part of factor analysis, is to find coefficients of the factor pattern (a_{ji} , b_j and e_j). Since a system of orthogonal (uncorrelated) factors, consistent with observed data and satisfying Equation 1, may be chosen in an infinite number of ways, the coefficients of the factor pattern cannot be uniquely determined. Consequently, many factor analysis techniques have been developed to extract factors and to transform the extracted factors in order to obtain the factor solutions most amenable to interpretation.

The factoring operation is usually done on dimensionless, standardized values of variables Z_j for all individuals i . The standardized variables have zero means and variances equal to unity. Using the notation of Equation 1, the composition of the unit variance of variable Z_j is defined as:

$$\sum_{i=1}^m a_{ji}^2 + b_j^2 + e_j^2 = 1 \quad (2)$$

where: $\sum_{i=1}^m a_{ji}^2$ = communality of variable Z_j defined as the proportion of the unit variance explained by m common factors

b_j^2 = specificity of the observed variable Z_j

e_j^2 = error variance associated with variable Z_j

Since e_j^2 is usually unknown, the sum of $(b_j^2 + e_j^2)$ represents the uniqueness of the observed variable, i.e., that proportion of the unit variance unexplained by common factors.

Factor analyses were performed using the SAS computer program package [8].

Three different extraction techniques were investigated:

- principal component analysis,
- principal factor analysis and
- maximum-likelihood factor analysis.

Detailed results are reported only for the principal component analysis because the results obtained by this technique appeared to permit the best interpretation of the resulting factor solution.

The model for principal component analysis can be obtained from the general linear factor model of Equation 1 by removing unique factors ($S_j + E_j$). Mathematically, the method of factor extraction using principal component analysis is identical to that used for principal factor analysis when this method is applied to a correlation matrix with unities on the diagonal (e.g., Table 1). This ensures that prior communality estimates of variable Z_j are equal to 1. The resulting factors give the best least-square estimates of the entire correlation matrix and each succeeding common factor accounts for the maximum obtainable amount of variation in the correlation matrix [9]. In other words, the factors are selected in a stepwise manner.

The indeterminacy of factor solutions may result in factors with loadings (i.e., a_{ji} coefficients) which may be difficult to interpret. This situation can be radically improved by rotating the axes of the reference frame on which the factors are measured. Since the objective of this research was to obtain simplified factors (rather than, for example, to obtain a simplified factor pattern of a variable) and to maintain orthogonality of the factors, the varimax method of rotation was used. The varimax method alters individual factor coefficients, as well as the variance explained by each factor, while the total variance explained by the rotated and the original factor patterns remains unchanged. The method also strives for a simplified factor solution

by making the small factor loadings approach zero and the large factor loadings approach unity [9,10].

DATA ANALYSIS

Factor analysis was carried out on distress manifestation data obtained for three MTC districts. The procedure used for collecting the distress data was referenced previously and their correlation matrix was presented in Table 1. The three MTC districts were selected with the intention of obtaining a representative sample of distress manifestations associated with conventional flexible pavements (asphalt concrete on top of granular material) subjected to a variety of traffic and environmental exposures. Nearly all asphalt concrete pavements on the King's Highways in the three districts (about 3000 centreline km) were included in the study.

The frequency of occurrence of distress manifestations in the three districts is illustrated in Figure 1 using the final values (sums of scaled values of density and severity) of the 15 distress variables. According to this figure, the most frequent distress was transverse cracking -- half, full and multiple -- which occurred, in one form or another, on about 90% of all sections. On the other hand, alligator transverse cracking occurred on only 2% of the sections.

The factor solution obtained by principal component analysis and rotated using the varimax method is shown in Table 2. Part (a) of Table 2 gives the rotated factor pattern for only five factors, or principal components, and thus gives results for a truncated component solution. The remaining 10 factors (there are 15 variables) were not included in the solution based on the Mineigan criterion which states that the variance explained by a factor included in the solution must be at least equal to unity [8]. The number of factors required to represent the 15 variables was also tested using maximum-likelihood analysis. The probability level based on the chi-square test for the hypothesis of five factors being sufficient was 0.026; for that of 6 factors the probability was 0.500. This also indicates that the five-factor model provides an appropriate representation of the data.

The entries of the factor pattern in Table 2(a) are the a_{ji} coefficients of

Equation 1. They are also regression coefficients between variables Z_j and factors F_m . These entries are referred to as factor loadings and theoretically can range from -1 to +1. The further the factor loading for a given variable is from 0, the more one can generalize from that factor to the variable.

Final communality estimates of the 15 variables explained by the five factors are given in part (b) of Table 2. These estimates, multiplied by 100, yield the percentage of the variance for a given variable, explained by the factors. With the exception of variables D and J (wheel track rutting, and pavement edge single and multiple cracking), the factors explained more than 50% of the variance. The best results were obtained for distortion (68.9%) and for pavement edge alligator cracking (68.7%).

Part c of Table 2 shows the variance explained by each factor. These variances are equal to factor eigenvalues and can be calculated as:

$$\sum_{j=1}^{15} (a_{jm})^2 \quad (3)$$

For example, the standardized variance for Factor 1 was equal to 3.035 and represented about 20% of the total variance. (The total variance for the 15 standardized variables is equal to 15). The variance explained by the five factors was 8.93 and accounted for about 60% of the total variance of the original 15 variables.

This 60% of the total variance explained by the five factors is reasonable, but not as high as may be desired. This indicates the following:

- a) Additional variables should be included in the analysis to better define the common factors. It should be mentioned that the 15 variables used in this study were obtained by compressing information originally given by 27 variables into 15 variables [2]. The reduction in the number of variables was achieved by combining two or three similar distresses into one. For example, the two original distress manifestation variables "rippling" and "shoving" were combined into one called "rippling and shoving". The analyses were done using the 15, rather than the 27 variables since only the 15 variables are now identified and evaluated during field surveys.

- b) The variables have a high degree of uniqueness. Because uniqueness consists of a specific variance and an error variance in unknown proportions, it may be interpreted in many ways. For example, by attributing the main portion of uniqueness to the specific variance, the results suggest that many distress manifestation variables tend to measure unique, specific pavement deterioration properties not common to other variables. On the other hand, by attributing the main portion of uniqueness to the error variance, the results indicate the presence of substantial measurement errors. The presence of these errors in the pavement distress rating process has been documented before [11]. The most likely interpretation is somewhere between these two extremes.

At any rate, the construction of five new, uncorrelated, hypothetical variables, which contain 60% of the information previously transported by the 15 original correlated variables, is a significant accomplishment, particularly in view of the purpose of the work which was to provide an aggregated, approximate, and practical basis for predicting distresses.

The effect of varimax rotation is graphically illustrated in Figure 2 which shows a plot of the factor pattern in the common-factor space of two dimensions represented by Factors 1 and 2. The actual factor space is 5-dimensional. The plot is an example of several possible projections of this space to a Cartesian co-ordinate system.

The varimax rotation strives to simplify factor solution by concentrating variable loadings on as few factors as possible. Considering for example variable H (centreline single and multiple cracking), its loadings before rotation were 0.67 on Factor 1 and 0.40 on Factor 2. After the rotation the corresponding loadings were 0.80 and 0.

INTERPRETATION OF FACTORS

An important step in factor analysis is interpretation of factor meanings. Factors are unobservable hypothetical variables and their identification and interpretation is based upon observations of which variables are, and which are not related to the factors and what these relationships may conceptually indicate. In other words, we are searching for possible quantitative distinctions based on statistical results as well as for qualitative distinctions based on intuitive evaluation of the underlying physical phenomena.

The basic guide for factor interpretation is provided by the coefficients of the factor pattern (factor loadings). These coefficients, as regression coefficients between factors and variables, reflect the importance of the factors in predicting the observed variables. To facilitate interpretation, a list of salient factor loadings is given in Table 3. The salient (or prominent) factor loadings were defined as correlation coefficients equal to or greater than 0.4. This guarantees that the correlations are statistically significant ($p < 0.025$) even after making allowances for the possibility of increased errors of orthogonally rotated factor solutions [9].

The main motivation for applying the technique to pavement distress data is its potential to explain the relationship among many variables in terms of more basic concepts. These concepts should, in turn, help to explain the overall problem. Pavement damage in Ontario occurs because of the following four basic load and environment related forces and characteristics called damage attributes:

- 1/ traffic loads
- 2/ temperature changes
- 3/ moisture effects
- 4/ construction flaws due to materials and construction techniques.

Ideally, for explanatory purposes, one should strive to construct the factors so that each factor combines and isolates the effects of only one of the above damage attributes. However, all damage attributes act on the pavement structure simultaneously in many complex ways. For example, a frost heave is the result of combined damage attributes of temperature changes, moisture effects, and construction flaws. On top, the resulting pavement damage is aggravated by traffic loads. The frost heave itself would be described by the MTC distress survey in terms of distortion and perhaps also in terms of several different types of cracking. For these reasons, the ideal explanatory solution, based on the factor loadings of Table 3, is difficult to achieve.

By way of introduction to interpreting and naming factors, Factor 4 is considered first. This factor has only two salient (statistically significant) factor loadings and both of them are with variables describing alligator cracking: longitudinal wheel track alligator cracking (0.71) and centreline alligator cracking (0.80, Table 3). The remaining 13 variables, do not have statistically significant loadings on Factor 4. It should also be noted that

the two variables with salient loadings on Factor 4 do not have salient loadings on any other factor. Thus, Factor 4 can be considered a factor describing alligator cracking. However, the 15 original variables contain two additional variables describing other types of alligator cracking not included in Factor 4: pavement edge alligator cracking, and transverse alligator cracking.

The first variable associated with alligator cracking -- transverse alligator cracking -- is rare (it occurs on less than 4% of the sections as shown in Figure 1) and was included, as discussed later, in Factor 5. The second variable, pavement edge alligator cracking, loads strongly only on Factor 2 (0.81) and thus appears to be unrelated to the two types of alligator cracking associated with Factor 4. It may be hypothesized that Factor 4 describes alligator cracking caused by pavement structural fatigue while Factor 2 describes alligator cracking caused by insufficient strength of the pavement edge typical for pavements with thin asphalt concrete surfaces. This assumption is supported by the next highest loading for Factor 2, which is single and multiple pavement edge cracking. The two types of pavement edge cracking (single and multiple, and alligator) are related with each other and with Factor 2, but are unrelated to fatigue cracking described by Factor 4. Factor 4 was thus named fatigue cracking and Factor 2 was named pavement edge cracking.

Factor 1 has high salient or statistically significant loadings on all four variables describing different types of single and multiple cracking (longitudinal wheel track, centre line, pavement edge, and transverse) and was named thermal cracking factor. Evidently, single and multiple pavement edge cracking contributes both to the thermal cracking factor (Factor 1) with a loading of 0.40 and to the pavement edge cracking factor (Factor 2) with a loading of 0.53. The variance of this variable must then be subjectively divided for interpretative purposes. Since the two factors are orthogonal, it may be hypothesized that one portion of the single and multiple pavement edge cracking is related to the same causes as, for example, the transverse and centreline cracking of Factor 1 which have been linked in the past to high asphalt concrete stiffness at low temperature and to other causes [12]. The other portion of the single and multiple pavement edge cracking, would then be hypothesized to be caused by the same causes as Factor 2, i.e., insufficient strength of the pavement edge. It is worth noting that the thermal cracking

is also associated with ravelling and coarse aggregate loss (loading of 0.44). This seems to indicate that the low asphalt content and stripping, usually associated with ravelling, also contributes to thermal cracking [13].

Factor 3 has the highest positive loading on flushing (0.72) and the highest negative loading on ravelling and coarse aggregate loss (-0.45). The two variables are related in the opposite directions. Flushing is associated with the absence of ravelling and coarse aggregate loss, while the ravelling and coarse aggregate loss tends to be associated with the thermal cracking factor (loading of 0.44). Other salient loadings of Factor 3 are for the variables rippling and shoving, distortion, and longitudinal meander and midlane cracking. For this reason, Factor 3 was named surface instability factor. It may be also noted that pavement damage caused by frost heaves is usually described in terms of distortion and longitudinal meander and midlane cracking. Both these variables are associated with Factor 3.

Longitudinal meander and midlane cracking is associated with both the surface instability factor (loading 0.41) and with the thermal cracking factor (loading 0.61). This again suggests, quantitatively, how the cause for this distress manifestation may be proportioned.

Factor 5 explained the lowest amount of variance (Table 2, Part c) and was the most difficult to interpret. It had high loadings from transverse alligator cracking (0.73) and from random cracking (0.70) and was named random cracking factor. The name random cracking was selected because the occurrence of transverse alligator cracking is very low compared even to that of random cracking, as shown in Figure 1. Transverse alligator cracking usually develops from a single transverse crack by formation of additional parallel cracks alongside the original crack and by subsequent gradual formation of an alligator pattern. It is probably caused by all four basic damage attributes described above. Transverse alligator cracking was only marginally related to the fatigue cracking factor (0.231 in Table 2).

In summary, the following factors were identified. They are listed in order of their contribution in explaining the sample variance, together with their possible causes:

Factor	Factor Name	Possible Principal Cause
1	thermal cracking	temperature changes, traffic loads
2	pavement edge cracking	effect of load on thin AC pavement
3	surface instability	construction flaws (frost heaves)
4	fatigue cracking	traffic load
5	random cracking	all causes

The factors can be viewed as uncorrelated fundamental operational representatives of all 15 distress manifestations. Since the factors are orthogonal, information provided by any given factor is uncorrelated and independent of that provided by any other factor or factors.

It is important to realize that factor analysis techniques lie somewhere between a science and an art [14]. Different analysts may use different techniques which yield somewhat different results and different researchers may interpret even the same results differently. Therefore, the above results should be viewed as one of the possible interpretations of statistical data. Nevertheless, they can also be explained in term of (qualitative) reasonableness of the basic physical phenomena involved.

FACTOR SCORES

The factors as hypothetical constructs can be also expressed in terms of the 15 observed variables. It is thus possible to characterize, quantify, and predict pavement distress manifestations in terms of the five fundamental uncorrelated factors rather than in terms of the 15 highly correlated original variables.

Table 4 gives a matrix of scoring coefficients which can be used to calculate factor values (scores), S_k , for individual observations by employing the following formula:

$$S_{ki} = \sum_{j=1}^n (S_{kj} \cdot Z_{ji}) \quad (5)$$

where: S_{ki} = factor score for factor k, and observation i
 S_{kj} = scoring coefficient for factor k and variable j
 Z_{ji} = value of variable j for observation i
 n = number of variables

The matrix of scoring coefficients can be roughly approximated by dividing factor loadings by factor eigenvalues. The factor scores estimated by the scoring coefficients are also uncorrelated for all practical purposes [8]. These scores can be used to characterize and quantify the state of visual pavement deterioration instead of the original 15 variables. For example, the factor score for the general cracking factor (Factor 1) is:

$$S_{1i} = 0.151 \cdot Z_{Ai} + 0.061 \cdot Z_{Bi} - 0.185 \cdot Z_{Ci} + \dots + 0.006 Z_{0i} \quad (6)$$

where subscripts A,B,C,...0 refer to variables (distress manifestations) defined in Tables 1 to 4, and subscript i identifies an observation. Thus, for example, Z_{Ai} is a value of ravelling and coarse aggregate loss for observation i, and Z_{Bi} is a value for flushing for the same observation.

Let's examine the concept of characterizing, quantifying and ultimately predicting visual pavement distresses in terms of factor scores starting again with Factor 4. Factor 4 was named fatigue cracking and its two variable loadings are unique: longitudinal wheel track alligator cracking and centre line alligator cracking have salient, or statistically significant, factor loadings only on Factor 4. Furthermore, both variables measure the same phenomenon of cracking and are measured on the same scale. It is thus possible to conclude that this type of fatigue cracking can be predicted independently of virtually any other distress manifestation. This, of course, has been a common practice in the past and the present results provide further statistical justification for the practice..

Factor 1, named thermal cracking, is affected by two variables which do not provide unique loadings (ravelling and coarse aggregate loss and pavement edge single and multiple cracking) as well as by heterogeneous variables -- variables which are measured on different scales and which generally measure different deterioration phenomena such as rutting and cracking. Overall, Factor 1 loadings indicate that it is not possible to examine and predict the associated variables in isolation. For example, ravelling and wheel track rutting both contribute to longitudinal wheel track cracking, transverse single and multiple cracking and to other distresses. The prediction of any one of these distresses, rutting for example, is questionable without taking into account the influence of the other distresses. Similarly, considering Factor 3 and its salient loading, it appears unattainable to predict roughness

(in terms of distortion, and rippling and shoving) without taking into account flushing and longitudinal meander and midlane cracking.

The prediction of factor scores overcomes the above limitations since the scores encompass the contributions of all relevant variables and provide uncorrelated fundamental measures of pavement visual distresses. It is also worth noting that if the factor scores are known (or predicted), the scoring coefficients of Table 4 can be also used to calculate values of the individual pavement distress variables.

CONCLUSIONS AND RECOMMENDATIONS

1. The evaluation of visible pavement distresses benefits from the application of factor analysis techniques. Factor analysis techniques can identify fundamental and uncorrelated categories of pavement distress manifestations and are useful in explaining and investigating relationships between highly correlated pavement distresses. As with any statistical procedure, factor analysis is a valuable tool only if used correctly. In addition, because of the skills required for factor interpretation, the successful user must have an in-depth technical knowledge of the problem domain.
2. Principal component analysis identified five basic independent factors which together explain about 60% of the variance previously explained by 15 observed variables. These five factors were named thermal cracking, pavement edge cracking, surface instability, fatigue cracking, and random cracking.
3. The results of factor analysis help to quantify statistically associations between various distresses (such as ravelling and cracking or distortion and flushing) in terms of more basic concepts. However, because of the interaction between the pavement damage attributes (e.g., traffic loads and temperature changes) and pavement structures, it was not possible to isolate the effects of the individual damage attributes (expressed as visible pavement surface distress manifestations) and assign them only to specific factors.
4. Due to the complex interdependency of individual pavement distresses, predictions of pavement distresses should be done in terms of the

fundamental factors (i.e., factor scores) rather than in terms of the traditional distresses. The prediction of pavement distresses in terms of five factor scores will provide sufficiently detailed data for the selection and timing of pavement rehabilitation treatments and for life-cycle economic analysis. For planning purposes, the separate prediction of pavement distresses in terms of the 15 pavement distress manifestation variables appears to be both impractical (because too many prediction models would be required) and logically incorrect (because distresses are interdependent).

5. All 15 distress manifestation variables currently used to characterize visible pavement deterioration contribute significantly to one or more of the fundamental factors and should be retained. Also, the individual distress variables are required for the selection of specific maintenance treatments and for establishing the existing values of the five factors.

ACKNOWLEDGEMENTS

The authors express their appreciation to members of the MTC Regional Geotechnical Sections for providing the pavement condition data which made this report possible. Appreciation is also extended to W.A. Phang, Manager of Pavement and Roadway Research, MTC, and to Dr. G.W. Bennett, Statistical Consulting Service, University of Waterloo, for many valuable comments and suggestions.

REFERENCES

- [1] Hudson, W.R., Finn, F.N., Pedigo, R.D., and Roberts, F.L., "Relating Pavement Distress to Serviceability and Performance," Report No. FWHA-RD-80-098, July 1980.
- [2] Hajek, J.J., Phang, W.A., Wrong, G.A., and Stott, G.M., "Pavement Condition Index (PCI) for Flexible Pavements," Report PAV-86-02, Ontario Ministry of Transportation and Communications, Downsview, Ontario, July 1986.
- [3] Hajek, J.J., "Life-Cycle Pavement Performance Modelling Using a Knowledge-Based Expert System Technology," unpublished report, Department of Civil Engineering, University of Waterloo, Waterloo, Ontario.
- [4] Hutchinson, B.G., "Principles of Subjective Rating Scale Construction," Highway Board Record No. 46, Washington, D.C., 1964, pp. 60-70.
- [5] Mulaik, S.A., "The Foundations of Factor Analysis," McGraw-Hill Book Company, 1976.
- [6] Harman, H.H., "Modern Factor Analysis," The University of Chicago Press, Chicago 60637, 1968.
- [7] Mouchahoir, G.E., "The Use of Multivariate Statistics in Transportation Planning," Traffic Engineering, October 1971, pp. 44-48.
- [8] SAS Institute Inc., "SAS User's Guide: Statistics, Version 5 Edition," SAS Institute, Cary, North Carolina, 1985.
- [9] Gorsuch, R.L., "Factor Analysis," Second Edition, Lawrence Erlbaum Associates, Inc., Hillsdale, New Jersey, 1983.
- [10] Harris, R.J., "A Primer of Multivariate Statistics," Academic Press, Inc., New York, New York 10003, 1975.

- [11] McHattie, R.L., and Connor, B.G., "Description and Evaluation of Alaska's Pavement Rating Procedure," Transportation Research Record 938, Transportation Research Board, Washington, D.C., 1985, pp. 61-72.

- [12] Hajek, J.J., and Haas, R.C.G., "Predicting Low Temperature Cracking Frequency of Asphalt Concrete Pavements," TRB Report 407, Transportation Research Board, Washington, D.C., 1972, pp. 39-54.

- [13] Marks, V.J., Huisman, C.L., "Reducing the Adverse Effects of Transverse Cracking," Final Report for Project HR-217, Iowa Department of Transportation, Ames, Iowa 50010, January 1985.

- [14] Dickinson, L.L., and Hall, J.W., "Factor Analysis of Pedestrian Accidents," Transportation Research Record 605, Washington, D.C., 1986, pp. 35-41.

Table 1/ Simple Correlation Matrix for MTC's 15 Distress Manifestations

VARIABLE NAME	A	B	C	D	E	F	G	H	I	J	K	L	M	N	O
A Ravelling & Coarse Aggregate Loss	1.000														
B Flushing	-0.042	1.000													
C Rippling & Shoving	-0.113	0.132	1.000												
D Wheel Track Rutting	0.238	0.084	0.040	1.000											
E Distortion	0.066	0.316	0.310	0.313	1.000										
F Long. Wheel Track- Single & Multiple Cracking	0.232	0.189	0.059	0.459	0.426	1.000									
G - Alligator Cracking	0.010	0.025	0.096	0.204	0.194	0.319	1.000								
H Centreline - Single & Multiple Cracking	0.272	0.062	-0.085	0.343	0.243	0.468	0.145	1.000							
I - Alligator Cracking	0.155	0.032	0.095	0.153	0.207	0.245	0.291	0.224	1.000						
J Pavement Edge - Single & Multiple Cracking	0.218	0.099	0.137	0.300	0.256	0.302	0.225	0.334	0.190	1.000					
K - Alligator Cracking	0.120	0.060	0.220	0.202	0.321	0.252	0.179	0.141	0.081	0.340	1.000				
L Transverse - Full, Half & Multiple Cracking	0.251	-0.002	-0.077	0.400	0.101	0.419	0.101	0.586	0.122	0.292	0.059	1.000			
M - Alligator Cracking	-0.006	-0.029	0.021	0.041	-0.023	0.056	0.158	0.081	0.139	0.146	0.105	0.096	1.000		
N Longitudinal Meander & Midlane Cracking	0.096	0.204	0.177	0.331	0.404	0.537	0.213	0.464	0.249	0.366	0.178	0.430	0.203	1.000	
O Random Cracking	0.048	0.047	0.079	0.148	-0.006	0.239	0.149	0.090	0.085	0.185	0.176	0.159	0.222	0.173	1.000

Note: Correlation coefficients are based on 347 observations and are significant at the 1% level if their value exceeds approximately |0.15|.

Table 2/ Varimax Solution for Principal Component Analysis

Part (a) Rotated Factor Pattern						Part (b) Final Communality Estimates ¹
VARIABLE NAME	FACTORS					
	1	2	3	4	5	
A Ravelling & Coarse Aggregate Loss	0.443	0.335	-0.455	0.036	-0.250	0.579
B Flushing	0.146	-0.018	0.719	-0.101	-0.049	0.551
C Rippling & Shoving	-0.214	0.448	0.492	0.143	0.062	0.553
D Wheel Track Rutting	0.595	0.284	0.054	0.095	-0.032	0.448
E Distortion	0.281	0.390	0.582	0.252	-0.236	0.689
F Long. Wheel Track- Single & Multiple Cracking	0.670	0.196	0.255	0.247	0.056	0.617
G - Alligator Cracking	0.094	0.143	0.049	0.708	0.184	0.567
H Centreline - Single & Multiple Cracking	0.796	-0.003	-0.008	0.115	0.018	0.648
I - Alligator Cracking	0.173	0.017	-0.019	0.802	-0.022	0.674
J Pavement Edge - Single & Multiple Cracking	0.399	0.527	0.009	0.131	0.180	0.486
K - Alligator Cracking	0.072	0.815	0.057	0.040	0.113	0.687
L Transverse - Full, Half & Multiple Cracking	0.805	-0.060	-0.080	-0.039	0.154	0.683
M - Alligator Cracking	0.038	-0.020	-0.048	0.231	0.731	0.592
N Longitudinal Meander Midlane Cracking	0.614	0.066	0.411	0.219	0.225	0.649
O Random Cracking	0.157	0.239	0.007	-0.069	0.703	0.581

Part (c) Variance Explained by Each Factor						
	FACTORS					Total ²
	1	2	3	4	5	
Variance Explained (Eigenvalues)	3.035	1.613	1.556	1.448	1.311	8.963
Percent of Total Variance	20.2	10.8	10.4	9.7	8.7	59.8

¹ One minus communality gives variable uniqueness.

² Total unit variance for 15 observations is equal to 15.

Table 3/ Salient Factor Loadings¹

VARIABLE NAME	Factor 1 Thermal Cracking	Factor 2 Edge Cracking	Factor 3 Surface Instability	Factor 4 Fatigue Cracking	Factor 5 Random Cracking
A Ravelling & Coarse Aggregate Loss	0.44		-0.45		
B Flushing			0.72		
C Rippling & Shoving		0.45	0.49		
D Wheel Track Rutting	0.60				
E Distortion		0.40	0.58		
F Long. Wheel Track- Single and Multiple Cracking	0.67				
G - Alligator Cracking				0.71	
H Centreline - Single and Multiple Cracking	0.80				
I - Alligator Cracking				0.80	
J Pavement Edge - Single and Multiple Cracking	0.40	0.53			
K - Alligator Cracking		0.81			
L Transverse - Full, Half & Multiple Cracking	0.81				
M - Alligator Cracking					0.73
N Longitudinal Meander Midlane Cracking	0.61		0.41		
O Random Cracking					0.70

¹ For factor loadings higher than 0.40.

Table 4/ Scoring Coefficients

VARIABLE NAME	Factor 1 Thermal Cracking	Factor 2 Edge Cracking	Factor 3 Surface Instability	Factor 4 Fatigue Cracking	Factor 5 Random Cracking
A Ravelling & Coarse Aggregate Loss	0.151	0.283	-0.396	-0.012	-0.260
B Flushing	0.061	-0.133	0.517	-0.161	-0.018
C Rippling & Shoving	-0.185	0.277	0.271	0.041	0.027
D Wheel Track Rutting	0.190	0.119	-0.030	-0.045	-0.082
E Distortion	0.021	0.153	0.316	0.093	-0.241
F Long Wheel Track- Single & Multiple Cracking	0.201	-0.019	0.113	0.057	-0.020
G - Alligator Cracking	-0.093	-0.017	-0.048	0.539	0.061
H Centreline - Single & Multiple Cracking	0.307	-0.129	-0.034	-0.018	-0.036
I - Alligator Cracking	-0.045	-0.115	-0.091	0.652	-0.112
J Pavement Edge - Single & Multiple Cracking	0.061	0.323	-0.095	-0.037	0.078
K - Alligator Cracking	-0.098	0.602	-0.093	-0.103	0.030
L Transverse - Full, Half & Multiple Cracking	0.336	-0.152	-0.060	-0.149	0.091
M - Alligator Cracking	-0.049	-0.093	-0.035	0.119	0.563
N Longitudinal Meander & Midlane Cracking	0.189	-0.145	0.252	0.028	0.134
O Random Cracking	0.006	0.125	-0.015	-0.187	0.551


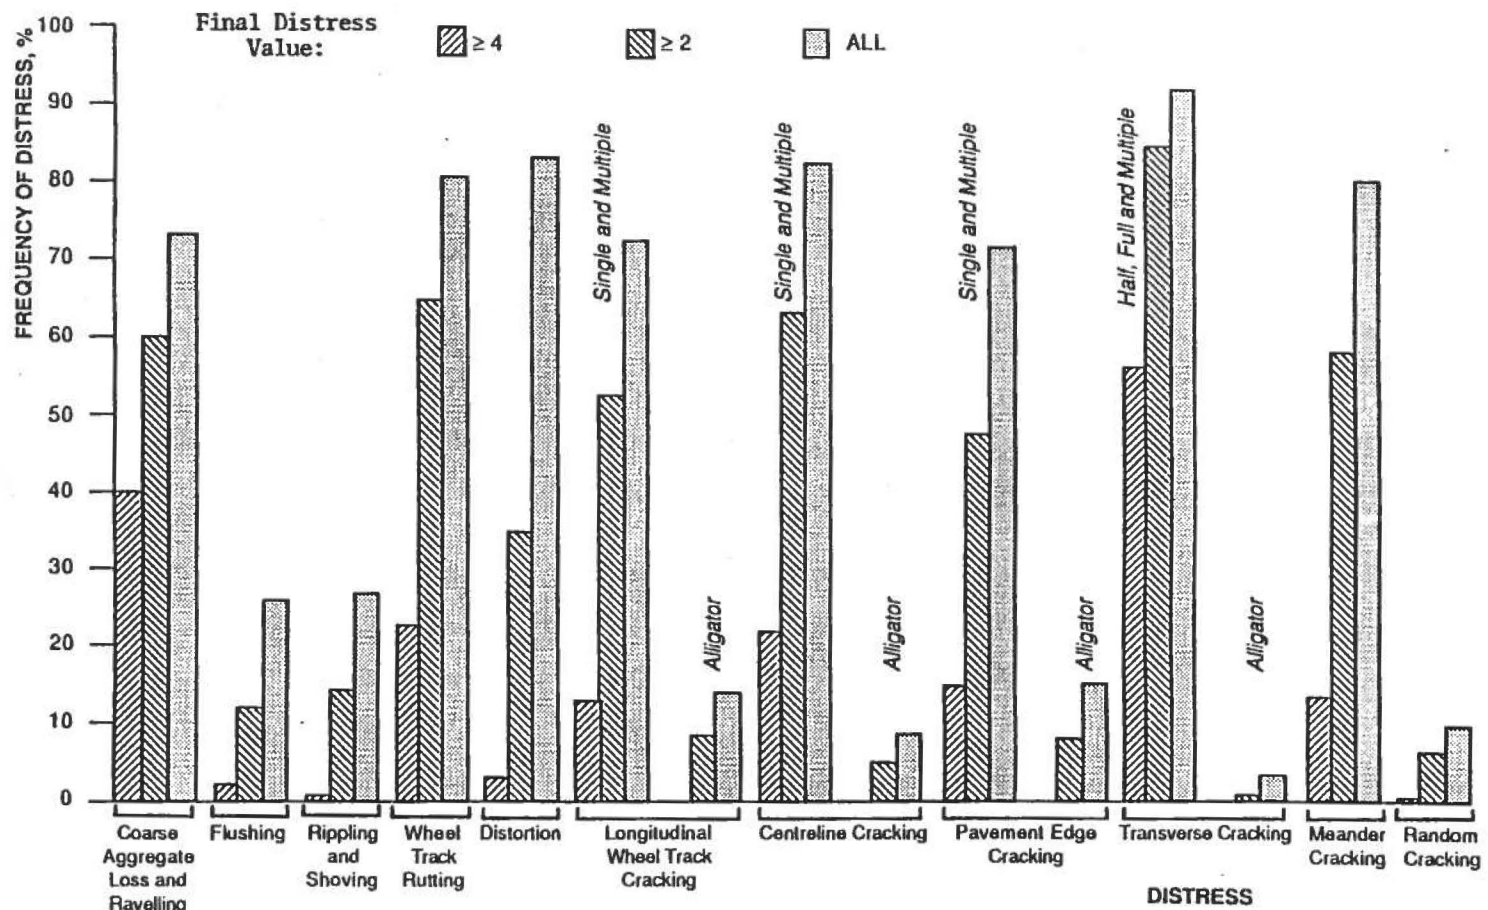


Figure 1/ Occurrence of Distress Manifestations

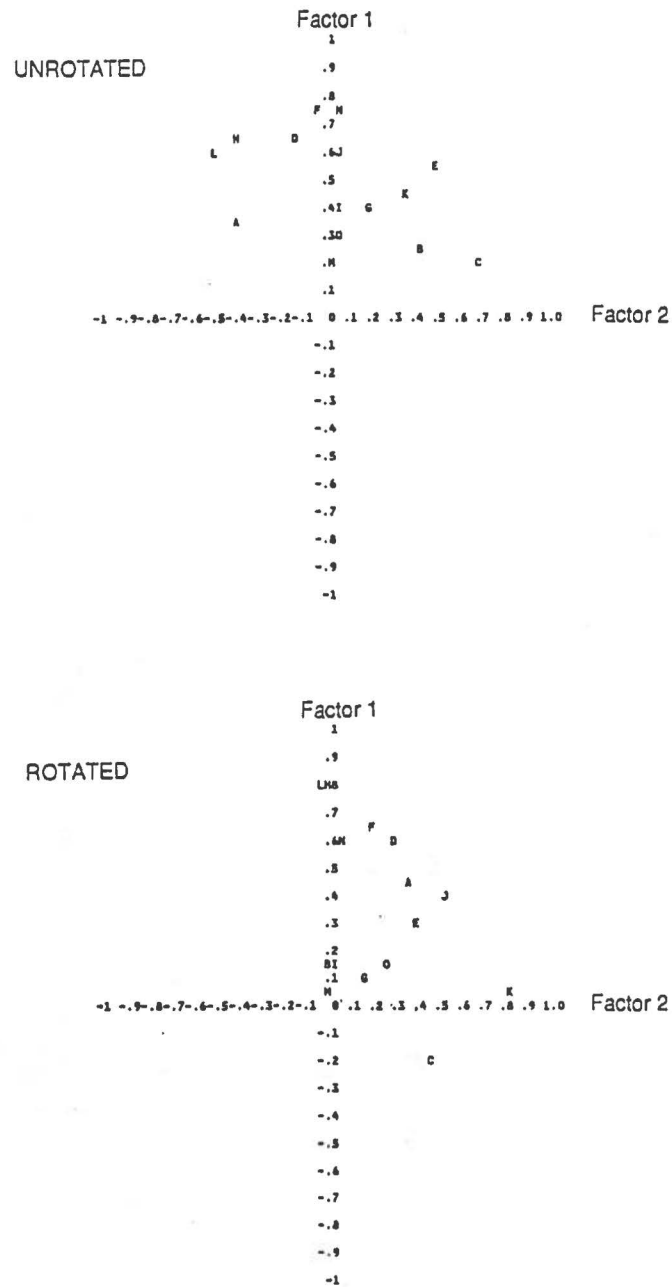

LEGEND

A,B,C...O are variables defined in Tables 1 to 4.

Figure 2/ Graphical Representation of Varimax Rotation